



# Strong enhancement of magnetic ordering temperature and structural/valence transitions in $\text{EuPd}_3\text{S}_4$ under high pressure

Shuyuan Huan<sup>a,b</sup>, Dominic H. Ryan<sup>c,1</sup>, Tyler J. Slade<sup>a,b</sup>, Barbara Lavina<sup>d,e</sup>, Greeshma Jose<sup>f</sup>, Haozhe Wang<sup>g</sup>, John M. Wilde<sup>a,b</sup>, Raquel A. Ribeiro<sup>a,b</sup>, Jiyong Zhao<sup>e</sup>, Weiwei Xie<sup>g</sup>, Wenli Bi<sup>h</sup>, Esen E. Alp<sup>e</sup>, Sergey L. Bud'ko<sup>a,b,1</sup>, and Paul C. Canfield<sup>a,b,1</sup>

Edited by J. C. Davis, University of Oxford, Oxford, United Kingdom; received June 26, 2023; accepted November 14, 2023

We present a comprehensive study of the inhomogeneous mixed-valence compound,  $\text{EuPd}_3\text{S}_4$ , by electrical transport, X-ray diffraction, time-domain  $^{151}\text{Eu}$  synchrotron Mössbauer spectroscopy, and X-ray absorption spectroscopy measurements under high pressure. Electrical transport measurements show that the antiferromagnetic ordering temperature,  $T_N$ , increases rapidly from 2.8 K at ambient pressure to 23.5 K at ~19 GPa and plateaus between ~19 and ~29 GPa after which no anomaly associated with  $T_N$  is detected. A pressure-induced first-order structural transition from cubic to tetragonal is observed, with a rather broad coexistence region (~20 GPa to ~30 GPa) that corresponds to the  $T_N$  plateau. Mössbauer spectroscopy measurements show a clear valence transition from approximately 50:50  $\text{Eu}^{2+}:\text{Eu}^{3+}$  to fully  $\text{Eu}^{3+}$  at ~28 GPa, consistent with the vanishing of the magnetic order at the same pressure. X-ray absorption data show a transition to a fully trivalent state at a similar pressure. Our results show that pressure first greatly enhances  $T_N$ , most likely via enhanced hybridization between the Eu 4*f* states and the conduction band, and then, second, causes a structural phase transition that coincides with the conversion of the europium to a fully trivalent state.

mixed valency | high-pressure effect | antiferromagnetism | structural transition | valence transition

In general, mixed valency in *f*-electron systems occurs when the more localized *f*-orbitals of rare-earth elements hybridize with *s*, *p*, and/or *d* electrons. In the presence of a small energy difference between competing valence states (even smaller than *f*-electron bandwidth), the system can fluctuate among these nearly degenerate states with different degrees of orbital valences. This phenomenon is commonly referred to as a fluctuating valence state (1). The onset of mixed-valence behavior under external pressure, chemical substitutions, or thermal contraction has dramatic consequences on the macroscopic properties of *f*-electron systems including lattice collapse (2), quenched magnetism (3), superconductivity (4, 5), Kondo behavior (6), and quantum criticality (4, 5). Despite being central to *f*-electron physics, the underlying mechanism of mixed-valence phenomena is still not fully understood due both to experimental limitations and to the lack of an adequate diversity of ideal materials.

That said, the inhomogeneous mixed-valence behavior of europium in  $\text{EuPd}_3\text{S}_4$  is rather special and offers the opportunity to study Eu mixed valency in a novel limit. The rare-earth palladium bronzes,  $\text{RPd}_3\text{S}_4$ , were reported to crystallize in the cubic  $\text{NaPt}_3\text{O}_4$  structure [ $Pm\bar{3}n$ , space group (SG) #223] with the rare earth occupying the  $2a$  site and forming a bcc sublattice (7). Whereas the  $\text{RPd}_3\text{S}_4$  compounds exist for all the trivalent rare earths, they do not appear to form with the divalent alkaline earths (Ca, Sr, ...). Interestingly, when prepared with europium (7) or ytterbium (8) a roughly 50:50 mix of divalent and trivalent rare earth was found, which makes the intermediate valence in these two compounds distinct from the more general fluctuating valence phenomenon case. In  $\text{EuPd}_3\text{S}_4$ , 50%  $\text{Eu}^{2+}$  makes the material magnetic as observed in Mössbauer spectroscopy and thermodynamic measurements (7, 9). By chemical substitution, smaller  $\text{Y}^{3+}$  ions tend to replace  $\text{Eu}^{3+}$  sites first and make the valence of Eu more divalent; however, substitution with bigger  $\text{La}^{3+}$  ions on the other hand, promotes the electron hopping between  $\text{Eu}^{2+}$  and  $\text{Eu}^{3+}$ , leading to an intermediate Eu valence until 60% of Eu have been replaced, above which, Eu becomes more trivalent. The chemical substitution work suggests that preservation of the unit cell volume size is a dominant factor controlling the  $\text{Eu}^{2+}:\text{Eu}^{3+}$  valence ratio (9). Very recently, it was found that rather than adopting the  $Pm\bar{3}n$  structure with a single, crystallographic Eu site ( $2a$ ) hosting the two Eu valences,  $\text{EuPd}_3\text{S}_4$  was found to take the more reasonable cubic  $Pm\bar{3}$  (SG #200) structure with two distinct Eu sites ( $1a$  and  $1b$ ) below 340 K at ambient pressure (10). As such then,  $\text{EuPd}_3\text{S}_4$  allows for

## Significance

The complexities of Ce- and Yb-based systems have been explored extensively and continue to attract attention. By contrast, the rich phenomenology of Eu-based systems remains largely understudied, despite the same potential for coupled valence, volume, electronic, and magnetic contributions. As we show here, the inhomogeneous mixed-valence  $\text{EuPd}_3\text{S}_4$  under hydrostatic pressure exhibits an eightfold increase of the Néel temperature followed by a structural transition to a lower symmetry structure that coincides with a transition to a fully nonmagnetic state. Our derived phase diagram differs significantly from the proposed global phase diagram for Eu compounds further emphasizing both the need for broader study and the opportunities Eu-based compounds present for developing insights into, and examples of, mixed-valent behavior.

Author contributions: D.H.R., S.L.B., and P.C.C. designed research; S.H., D.H.R., T.J.S., B.L., G.J., H.W., R.A.R., J.Z., W.X., W.B., E.E.A., S.L.B., and P.C.C. performed research; S.H., D.H.R., B.L., J.M.W., W.B., E.E.A., S.L.B., and P.C.C. analyzed data; T.J.S., B.L., G.J., H.W., J.M.W., R.A.R., J.Z., W.X., W.B., and E.E.A. provided valuable discussion on results and manuscript; and S.H., D.H.R., S.L.B., and P.C.C. wrote the paper.

The authors declare no competing interest.

This article is a PNAS Direct Submission.

Copyright © 2023 the Author(s). Published by PNAS. This article is distributed under Creative Commons Attribution-NonCommercial-NoDerivatives License 4.0 (CC BY-NC-ND).

<sup>1</sup>To whom correspondence may be addressed. Email: dominic.ryan@mccgill.ca, budko@ameslab.gov, or canfield@ameslab.gov.

This article contains supporting information online at <https://www.pnas.org/lookup/suppl/doi:10.1073/pnas.2310779120/-DCSupplemental>.

Published December 19, 2023.

the study of valence changes in an inhomogeneously mixed-valence system.


We considering that chemical substitution and the associated changes in unit cell were shown to profoundly impact the mixed-valence state in  $\text{EuPd}_3\text{S}_4$ , it is worthwhile to appreciate that the effect of external pressure has proven to be an effective way to tune the atomic distances and thus may be used to increase the degree of orbital hybridization, and is considered to be a cleaner and more powerful tool for modifying the valence state than chemical doping. Here, we report the systematic high-pressure investigation of  $\text{EuPd}_3\text{S}_4$  using a combined experimental approach including electrical transport measurements, X-ray diffraction (XRD), time-domain synchrotron Mössbauer spectroscopy (SMS) (11), and partial fluorescence-yield X-ray absorption spectroscopy (PFY-XAS). A significant, about eightfold, enhancement in antiferromagnetic transition temperature, ( $T_N$ ) from  $\sim 2.8$  K at ambient pressure (7) to  $\sim 3.5$  K at  $\sim 19$  GPa is observed. Subsequently, in a pressure window from  $\sim 19$  GPa to  $\sim 29$  GPa,  $T_N$  is almost pressure independent, whereas the size of the resistance drop below  $T_N$  is gradually suppressed with increasing pressure. The sample in this pressure window is found to be in a mixed phase of cubic and tetragonal structures with the ratio of cubic/tetragonal decreasing with increasing pressure. Above  $\sim 29$  GPa, an abrupt disappearance of antiferromagnetic (AFM) order is observed. In the same pressure range, both SMS and XAS measurements show a clear change from 50:50  $\text{Eu}^{2+}:\text{Eu}^{3+}$  to fully  $\text{Eu}^{3+}$  and is coincident with the complete disappearance of the lower pressure, cubic phase, resulting in a single phase of the non-moment-bearing tetragonal structure. This comprehensive study beautifully illustrates the interplay of crystal structure, magnetic ground state, and the associated valence state tuned by high pressure and suggests that  $\text{EuPd}_3\text{S}_4$  provides a clean and simple system for the detailed study of how magnetism, valence, and structure are intertwined and should serve as a benchmark for theoretical efforts to model and understand mixed-valence behavior.

## Results

Fig. 1A presents the temperature dependence of the resistance,  $R(T)$ , of single crystalline  $\text{EuPd}_3\text{S}_4$  under pressure up to  $\sim 32$  GPa. The overall  $R(T)$  behavior is metallic over the whole temperature

and pressure ranges covered here. A clear resistance drop is seen below 2.8 K at 0.4 GPa, reflecting the loss of spin disorder scattering as antiferromagnetic (AFM) ordering occurs. We define the Néel temperature,  $T_N$ , as the mid-point of the step in the temperature derivative of resistance ( $dR/dT$ ), with the uncertainty taken as half of the step width, as shown in Fig. 1B.  $T_N$  at 0.4 GPa is consistent with the ambient pressure heat capacity and magnetization results reported previously (7, 9). Increasing the pressure from 0.4 GPa to  $\sim 19$  GPa leads to a marked rise in  $T_N$  from 2.8 K to 23.5 K, Fig. 1D. Above 20 GPa, there is a sharp increase in resistance; the position of the  $T_N$  step remains essentially unchanged, but the size of the step-like feature in  $dR/dT$  becomes progressively smaller and is lost by  $\sim 29$  GPa (Fig. 1B). As will be shown below, when we examine the powder X-ray data, these changes are consistent with the observation that for  $\sim 19$  to 29 GPa, the system passes through a crystallographic two-phase region as the increasing pressure progressively converts the AFM-ordering  $\text{Eu}^{2+}$ -containing phase into a fully trivalent nonmagnetic phase. Above  $\sim 29$  GPa, the features marking loss of spin-disorder scattering in the resistance, associated with the step like feature in  $dR/dT$  are gone, and no further evidence for magnetic ordering (at least above 1.8 K, our lowest measurement temperature) is observed, suggesting that the conversion is now complete. In addition to the step like feature that is related to  $T_N$ , a slope change in  $dR/dT$  at lower temperature (marked as  $T^*$ , in Fig. 1B) is also observable at and above 12 GPa and becomes clearer as pressure increases to  $\sim 19$  GPa (Fig. 1B). Similar features in  $dR/dT$  are common in rare-earth-bearing compounds and are often associated with incommensurate-to-commensurate transitions or spin reorientations (12, 13). Of note is that the shape of the higher temperature  $R(T)$  curve clearly changes from concave-like at low pressures to convex-like at high pressures, indicating possible change of band structure and/or paramagnetic and phonon scattering.

The Néel temperature,  $T_N$ , and anomaly,  $T^*$ , as functions of the pressure for  $\text{EuPd}_3\text{S}_4$  are presented in Fig. 1D. We can see that with increasing pressure,  $T_N$  has an approximately eightfold enhancement from 2.8 K at 0.4 GPa to around 23.5 K at  $\sim 19$  GPa with an average increasing rate of  $\sim 1.1$  K/GPa, then  $T_N$  remains essentially constant from  $\sim 19$  GPa to  $\sim 29$  GPa, above which signatures of antiferromagnetic ordering are not observed.

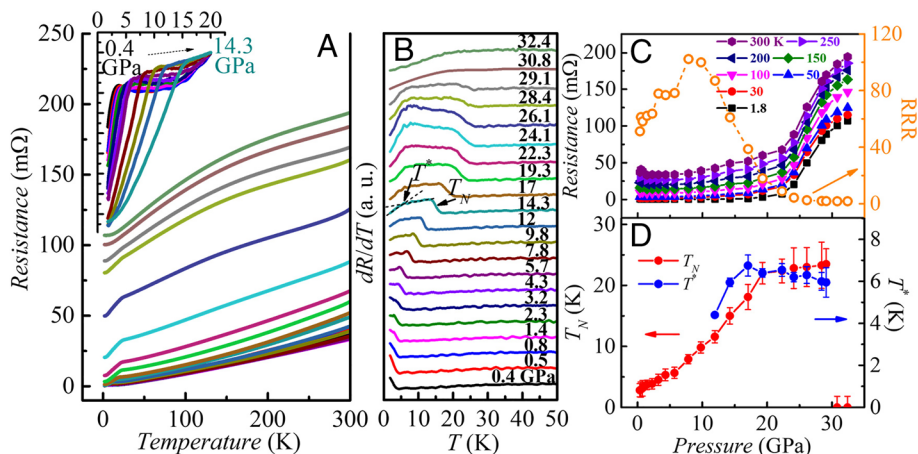

**Fig. 1.** Pressure dependence of electrical resistance and  $T_N$ . Temperature dependencies of the (A) electrical resistance and (B) temperature derivatives of the resistance for single crystal  $\text{EuPd}_3\text{S}_4$ , measured at different pressures. (A) and (B) share the same legend. The *Inset* in (A) shows the zoomed-in curves normalized at 20 K from 0.4 GPa to 14.3 GPa so as to better show the evolution of  $T_N$  below 14.3 GPa. In (B), curves at various pressures are offset from each other so as to better show the evolution of  $T_N$ .  $T_N$  is determined as the midpoint of the  $dR/dT$  shoulder, and  $T^*$  is defined as the intersection of two black dashed lines drawn from high temperature and low temperature. (C) Resistance at various temperatures and the residual resistivity ratio (RRR) as functions of pressure. (D)  $T_N$  and  $T^*$  as functions of pressure.


Meanwhile, resistance versus pressure (Fig. 1C) at all temperatures shows an abrupt increase starting from  $\sim 22$  GPa. This is most likely due to the onset of a crystallographic two-phase region (as will be discussed below) but may also be associated with the commensurate change in valence and therefore band structure. As will be discussed further below, the flat  $T_N$  versus  $P$  region between  $\sim 19$  GPa and  $\sim 29$  GPa is most likely the result of entering a region of mixed crystallographic phases with increasing pressure leading to a larger fraction of the smaller volume, purely  $\text{Eu}^{3+}$  phase. As a result of this two-phase nature, we speculate that the strain on the remaining  $\text{Eu}^{2+}$  phase remains effectively constant over this pressure range, leading to an effectively constant  $T_N$  value. Remarkably,  $T^*$  exhibits very similar behavior, rising with  $T_N$  and then becoming constant through the two-phase region, reinforcing the idea that in the two-phase region, there is relatively little change in strain on the  $\text{Eu}^{2+}$  fraction of the sample.

It is notable that the residual resistance ratio [ $\text{RRR} = R(300\text{ K})/R(1.8\text{ K})$ ] as a function of the pressure shows a different behavior compared with the resistance as a function of the pressure, as shown in Fig. 1C. The  $\text{RRR}$  first increases from  $\sim 40$  at 0.4 GPa to  $\sim 100$  at  $\sim 10$  GPa and then rapidly decreases to less than 2 at  $\sim 22$  GPa, above which the resistance at all temperatures shows a sharp increase with the pressure, which might indicate a structural transition. Fig. 1C also presents the pressure-dependent resistance of the sample at representative temperatures ranging from 1.8 K to 300 K. Each dataset shows a marked increase in resistance at  $\sim 24$  GPa indicating that in the temperature range we measured, if there is any structural/valence transition under pressure, the transition temperature should be above 300 K and its phase line is (almost) vertical in temperature–pressure ( $T$ – $P$ ) plot.

To explicitly explore the structural stability of  $\text{EuPd}_3\text{S}_4$  under pressure, synchrotron powder X-ray diffraction (PXRD) experiments were performed on a sintered powder (polycrystalline) sample up to  $\sim 57$  GPa. Fig. 2A–C demonstrates the outcomes. Peaks from copper (calibrant) and rhenium (gasket) are indexed in Fig. 2B and C and are marked with pink stars and blue crosses,

respectively, in *SI Appendix, Fig. S1* to illustrate their systematic shift with pressure. Three distinct pressure regions were detected, as shown in Fig. 2A: zone I (ambient to  $\sim 17$  GPa), zone II ( $\sim 20$  GPa to  $\sim 32$  GPa), and zone III ( $\sim 34$  GPa to  $\sim 57$  GPa), respectively. The diffraction patterns in zone I can be indexed to the cubic space group  $Pm\bar{3}$  (SG #200), as shown in Fig. 2B, which is consistent with the structure of the specimen at ambient pressure (10). In zone III, the patterns are resolvable different and could be assigned to a tetragonal space group,  $P4/mmm$  (SG #123), as depicted in Fig. 2C. The pressure dependencies of the lattice parameters and unit cell volume  $\text{EuPd}_3\text{S}_4$  are shown in Fig. 2D and E. Clear discontinuous changes in both lattice parameters ( $a$  and  $c$ ) and the unit cell volume ( $V$ ) are observed. Considering that  $P4/mmm$  (SG #123) is not a translationengleiche subgroup of  $Pm\bar{3}$  (SG #200), which is actually a translationengleiche subgroup of  $Pm\bar{3}n$  (SG #223), we expect that the structural transition under pressure to be first order according to Hermann's theory (14, 15). The pressure–volume,  $P(V)$  curve in zone I was analyzed using a second-order Birch–Murnaghan equation of state (BM EOS) as shown in Fig. 2E. For pressures up to  $\sim 18$  GPa (zone I), the elastic parameters yield a zero-pressure bulk modulus  $B_0$  of 103.5(20) GPa and a zero-pressure unit-cell volume  $V_0$  of 297.89  $\text{\AA}^3$  at ambient conditions which is consistent with the reported value (9). The unit cell volume in zone III shows a clear deviation from the fitted curve based on the data points in zone I with the unit cell volume at  $\sim 34$  GPa decreasing by  $\sim 4.8\%$ , which is intricately linked to the structural transition and the substantial change in the valence of Eu ions. It is worth mentioning that the fitted parameters in zone I were also obtained from a larger volume of data taken from multiple experimental runs, as shown in *SI Appendix, Fig. S5*.

As diffraction peaks from both the cubic and tetragonal phases are observed in zone II, a two-phase scenario is a reasonable interpretation. The gradual disappearance of the cubic phase and the

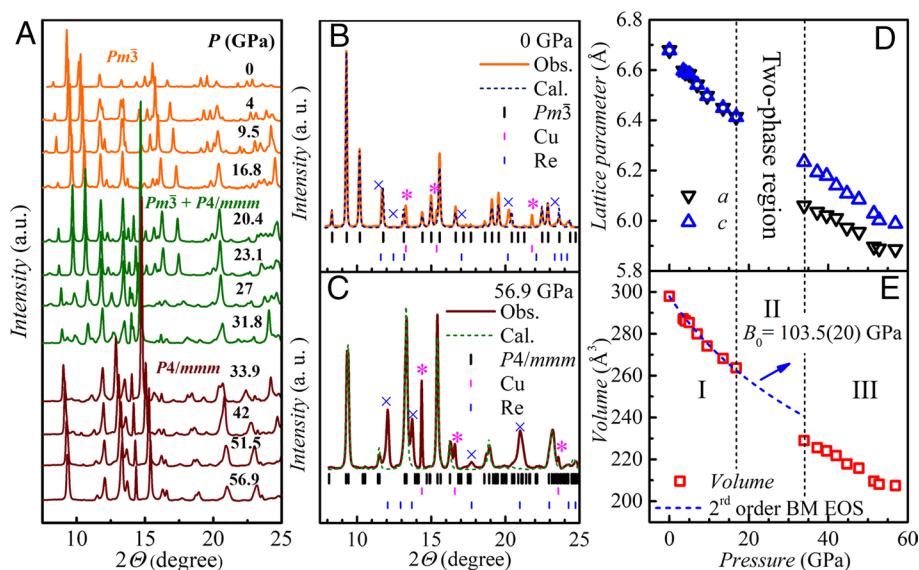

**Fig. 2.** Pressure induced structural phase transition. (A) Selective powder X-ray diffraction (PXRD) patterns of  $\text{EuPd}_3\text{S}_4$  at various pressures from 0 GPa to 56.9 GPa. The synchrotron X-ray wavelength  $\lambda$  is 0.4833  $\text{\AA}$ . The data were collected at room temperature. The full set is shown in *SI Appendix, Fig. S1*. (B) Rietveld refinement of the PXRD pattern at ambient pressure. (C) Le Bail fit to the high-pressure  $P4/mmm$  structure at 56.9 GPa. The pink stars and blue crosses in (B) and (C) represent the clear extra peaks in the PXRD spectra of copper (pressure manometer) and rhenium (gasket), respectively. (D) Pressure dependences of the refined lattice constants  $a$  and  $c$ . (E) Pressure dependence of the unit cell volume. The blue dashed curve shows the fitting by second-order Birch–Murnaghan equation of state (BM EOS). Several sets of independent PXRD measurements in zone I have been performed and show the same evolution of volume with the pressure. A more detailed plot is shown in *SI Appendix, Fig. S5*.

appearance and growth of the tetragonal phase can be seen clearly despite the increasing difficulty of indexing the diffraction patterns within zone II. Fig. 3 shows the changes of the specific diffraction peaks in detail, highlighting the disappearance of the cubic (210) and (211) Bragg peaks and the sudden emergence of the tetragonal (113) peak at  $\sim 20$  GPa. *SI Appendix, Figs. S2–S4* show more detail.

A first-order structural phase transition typically involves a sudden change in lattice parameters and unit cell volume, and the presence of a two-phase region in the intermediate pressure zone. Fig. 2 *D* and *E* illustrate all these features clearly. However, the large two-phase window, more than 10 GPa, cannot simply be attributed to pressure gradients within the pressure transmitting medium since the pressure gradient in neon at 20 GPa is only 0.15 GPa (16), which is almost two orders of magnitude smaller than the observed two-phase pressure range. The broad two-phase region must therefore be considered to be an intrinsic feature associated with the valence change in  $\text{EuPd}_3\text{S}_4$  under these conditions. An analogous large two-phase pressure range has also been reported in  $\text{SmSe}$ ,  $\text{SmTe}$  (17), and  $\text{CaFe}_2\text{As}_2$  (18, 19), possibly as a result of anharmonic strain effects caused by the significant volume mismatch between the various phases (20). Noteworthy, the Néel temperature plateau in Fig. 1*D*, where  $T_N$  (and  $T^*$ ) are almost independent of pressure, coincides well with the two-phase pressure region that has a mixed phase with shifting phase ratio. In other words, the behavior of the  $T_N$  plateau and the gradual loss of magnetic moment in the  $T_N$  plateau region are likewise intrinsic and may be closely related to the gradual increase in the relative amount of the tetragonal phase, and as will be shown below, nonmagnetic- $\text{Eu}^{3+}$ .


The conventional, energy-domain,  $^{151}\text{Eu}$  Mössbauer spectrum of  $\text{EuPd}_3\text{S}_4$  shows two, roughly equal-area, well-separated lines from the  $\text{Eu}^{2+}$  and  $\text{Eu}^{3+}$  present (7, 9). These two lines reflect the

two different transition energies (i.e., isomer shifts), and hence photon frequencies, associated with the two europium valence states. In the time-domain synchrotron Mössbauer spectroscopy (SMS) (11) spectra we observe a simple beat pattern between these two photon frequencies (see Fig. 4*A* at 0.7 GPa) with the beat frequency set by the fractional difference in photon energies (or frequencies), and the amplitude set largely by the relative populations of the two valence states. A visual inspection of Fig. 4*A* reveals that both change with increasing pressure: the beat frequency decreases, and the amplitude modulation generally becomes less distinct. The evolution in beat frequency indicates that the isomer shift difference between the two components is becoming smaller. Finally, there is an abrupt change in the curves above 27 GPa to a relatively very long beat period (rather than the simple exponential decay that we would associate with a single trivalent line) suggesting that the system is not just a cubic crystallographic phase with pure  $\text{Eu}^{3+}$ .

More intuitive energy-domain spectra generated by CONUSS (21) by fitting the time-domain data are shown in Fig. 4*B*. Within the pressure range of 0.7 GPa to 27 GPa, two distinct peaks are observed, representing the isomer shifts of  $\text{Eu}^{2+}$  and  $\text{Eu}^{3+}$  at low pressures. For clarity, these two peaks are referred to as the  $\text{Eu}^{2+}$  and  $\text{Eu}^{3+}$  peaks, although it should be noted that the oxidation state of the  $\text{Eu}^{2+}$  peak tends to approach that of  $\text{Eu}^{3+}$  under pressure. The intensity of the  $\text{Eu}^{2+}$  peak weakens around 27 GPa and vanishes at 29.7 GPa, resulting in the sole presence of the  $\text{Eu}^{3+}$  peak, thereby indicating a complete transition from an initial nearly 50:50  $\text{Eu}^{2+}$ :  $\text{Eu}^{3+}$  state to a fully  $\text{Eu}^{3+}$  state. Concurrently, the linewidth of  $\text{Eu}^{3+}$  peak exhibits a clear broadening at 29.7 GPa compared to lower pressures. This can be attributed to the presence of a quadrupole interaction,  $\Delta E(Q)$ , of 2.16(5) mm/s. This observation is consistent with the structural transition from a cubic to a tetragonal phase, where an electric field gradient develops as a result of the reduced symmetry. However, due to the crowded arrangement of multiple components split by the quadrupole interaction within the line width of  $\sim 2.3$  mm/s, the absorption spectrum is not resolved. Furthermore, the quadrupole interaction,  $\Delta E(Q)$ , increases within the pressure range of approximately 28 to 30 GPa, as shown in *SI Appendix, Fig. S6*. This increase can be attributed to the increase of structural anisotropy. The observed enhancement in the quadrupole interaction may correspond to the transition from a two-phase region, characterized by the presence of strain between the two phases, to a fully tetragonal phase. Upon decompression, the absorption peak corresponding to  $\text{Eu}^{2+}$  recovers at  $\sim 25$  GPa, indicating the reversibility of the pressure-driven transition.

The isomer shift exhibited the same evolution with pressure in a second experimental run on a sintered powder sample (SMS data are shown in *SI Appendix, Fig. S7*) as it did for a single crystal sample. Absolute calibration of the isomer shifts of the two components was achieved by measuring SMS spectra at several pressures after introducing a standard ( $\text{EuS}$ ) with a known isomer shift ( $-11.496$  mm/s) in the beam after the pressure cell (detailed explanation of calibration of absolute values of isomer shifts is shown in *SI Appendix, Figs. S8 and S9*). These corrected measurements allowed us to show that most of the isomer shift change is due to the  $\text{Eu}^{2+}$  line moving to more positive values (Fig. 4*C*) with increasing pressure.

The pressure dependence of the area fraction of the  $\text{Eu}^{2+}$  peak is plotted in Fig. 4*D*. There are some differences between the powder and single crystal data in the  $\sim 21$  to 27 GPa pressure range which are not surprising given their different microstructures and internal strain distributions. The pressure dependence of the mean Eu valence was estimated by assuming that the area of each

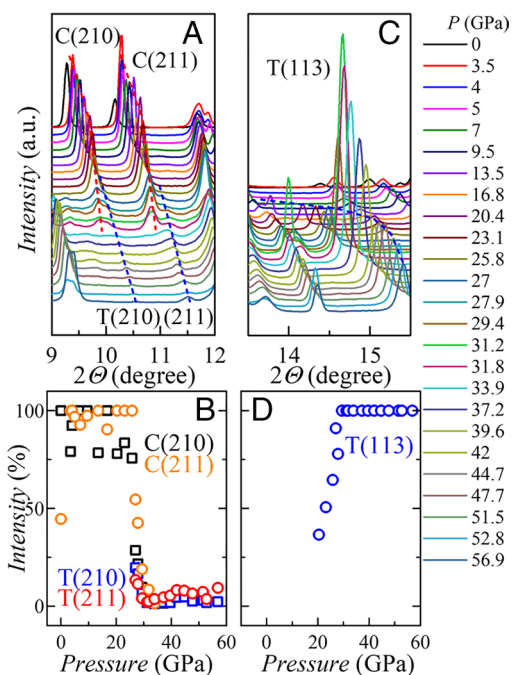

**Fig. 3.** The evolution of diffraction peaks with the pressure in selected 20 ranges. (A), (B) the cubic phase (210) and (211) (“cubic” is identified by “C”) to tetragonal (210) and (211) (“tetragonal” is identified by “T”); (C), (D) the emergence of T(113). (A) and (C) share the same legend. The red and blue dashed curves in (A) and (C) are the smooth guides to the eye of the position change of diffraction peaks. The percentage of the intensities in (B) and (D) are estimated by: (intensity of peak)/(maximum peak intensity in the spectrum).

component in the SMS spectrum was proportional to the number of ions associated with the corresponding valence state. The detailed calculation is shown in *SI Appendix, Fig. S10*, and the result is summarized in Fig. 5D, shown below.

Partial fluorescence-yield X-ray absorption spectroscopy (PFY-XAS) measurements were performed to provide independent confirmation of the valence change. As shown in Fig. 6A, the absorption peak corresponding to  $\text{Eu}^{2+}$  gradually weakens as the pressure increases to 14 GPa, then becomes much weaker at  $\sim 22$  GPa, and remains as a small bump for higher pressures, clearly demonstrating a transition from 50:50  $\text{Eu}^{2+}:\text{Eu}^{3+}$  to essentially  $\text{Eu}^{3+}$ . The valence transition appears at a somewhat lower pressure in the PFY-XAS measurements than in the SMS results. Such a shift may be associated with nonhydrostaticity due to the lack of a pressure transmitting medium (PTM) in the PFY-XAS measurement. The persistence of a tiny  $\text{Eu}^{2+}$  peak at higher pressures may be attributed to pressure inhomogeneity. Furthermore, a small, but discernible shift toward slightly lower energy of the absorption peak corresponding to  $\text{Eu}^{3+}$  is noted at and above  $\sim 22$  GPa. The possible reasons for this tiny shift in the absorption peak position, aside from experimental factors such as energy resolution and XAS instrument calibration, could be a change in the crystal field, which splits the  $4f$  electronic state into different energy levels. This shift could be closely related to the structural transition that begins to occur between  $\sim 20$  GPa and  $\sim 32$  GPa. To fully comprehend the mechanism behind the absorption peak shift, additional research, such as DFT calculation based on the more accurate structure, is required.


Modeling the PFY-XAS data using a series of Lorentzian and arctangent functions for each absorption peak, as seen in Fig. 6B, yields the mean valence of the Eu ion. The average valence is estimated using the following formula:

$$v = \frac{2 \times A_{\text{Eu}^{2+}} + 3 \times A_{\text{Eu}^{3+}}}{A_{\text{Eu}^{2+}} + A_{\text{Eu}^{3+}}}, \quad [1]$$


where  $A_{\text{Eu}^{2+}}$  and  $A_{\text{Eu}^{3+}}$  are the areas of absorption peaks for  $\text{Eu}^{2+}$  and  $\text{Eu}^{3+}$ , respectively. The estimated mean Eu valence as a function of pressure as measured by SMS and XAS are depicted in Fig. 5D and (Figs. 5E and 6C), respectively. Both measurements demonstrate a clear valence change from  $\text{Eu}^{2+}$  to  $\text{Eu}^{3+}$ . The shift is abrupt and occurs at higher pressure ( $> \sim 27$  GPa) in the SMS measurements with He as the PTM. Due to the low data density and the fact that the high-pressure XAS measurement is conducted without PTM, it is not possible to determine the width of the valence transition; however, it is clear that the mean valence is very close to  $3+$  at and above 24 GPa.

## Discussion

The pressure dependence of the AFM transition temperature  $T_N$ , resistance at 1.8 K, the volume of the unit cell, and the mean valences estimated from SMS and PTM data is presented in Fig. 5. Two vertical lines at  $\sim 20$  and 30 GPa mark the lower and upper boundaries of the two-phase region and are shown crossing all the datasets. Although the use of different PTMs and manometers for different high-pressure measurements made at different temperatures may cause some inconsistency in the critical pressures and possible smearing of the first-order transition, a clear picture still can be obtained: There are three distinct pressure regions associated with i) the low-pressure cubic phase, ii) an intermediate pressure two-phase region where both cubic and tetragonal phases are present, and finally iii) the high-pressure tetragonal phase (Fig. 5C). Two pressures ( $\sim 20$  GPa and  $\sim 30$  GPa) separate the changes we see in the  $T$ - $P$  phase diagram shown in Fig. 5A as well as the  $R(1.8\text{K})$  data shown in Fig. 5B. Fig. 5A shows that  $T_N$  rises rapidly in the low-pressure region, is essentially constant in the intermediate pressure region, and is not detectable (due to the loss of moment-bearing  $\text{Eu}^{2+}$ ) in the high-pressure region. Fig. 5B shows that the 1.8 K resistance of the low-pressure phase is

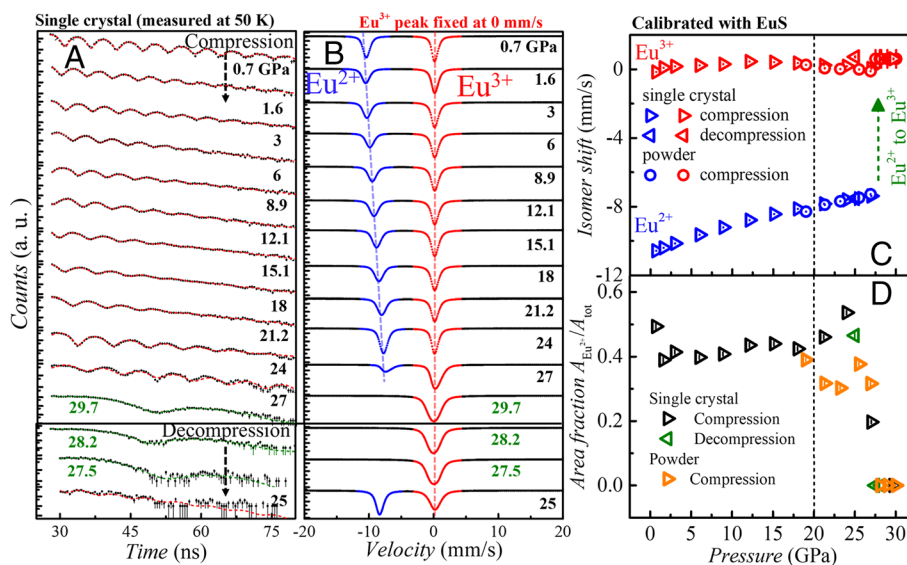


**Fig. 4.** Pressure-induced Eu valence transition from the isomer shift measurements. (A) The time domain  $^{151}\text{Eu}$  Synchrontron Mössbauer spectroscopy spectra (SMS) of  $\text{EuPd}_3\text{S}_4$  at 50 K under various pressures taken using a single crystal sample with helium as the pressure transmitting medium. The pressure was measured at 50 K. Pressure was first increased from 0.7 GPa to 29.7 GPa, and then decreased to 25 GPa, in order to assess the reversibility of the pressure and the valence transition. The red dotted curves are fit to the SMS spectra using CONUSS (21). (B) Simulated energy-domain Mössbauer spectra based on the fitting results from each corresponding SMS spectrum. For these simulated patterns, the isomer shift of the  $\text{Eu}^{3+}$  peak was fixed to zero and only changes in the isomer shift and weight of the  $\text{Eu}^{2+}$  peaks are apparent. In (B), the blue and red dashed lines serve as visual aids to illustrate the evolution of  $\text{Eu}^{2+}$  isomer shift while  $\text{Eu}^{3+}$  remains fixed. The calibrated (using the EuS standard) pressure dependence of the absolute isomer shifts for the  $\text{Eu}^{2+}$  and  $\text{Eu}^{3+}$  peaks are shown for both samples in (C), while (D) shows the pressure dependence of the  $\text{Eu}^{2+}$  area fraction. The absolute value of isomer shift is calibrated by moving a reference sample (EuS, at room temperature and ambient pressure, with known isomer shift of  $\text{Eu}^{2+}$  at  $-11.496$  mm/s) on the beam line. The detailed calibration process is explained in *SI Appendix, Figs. S8 and S9*.

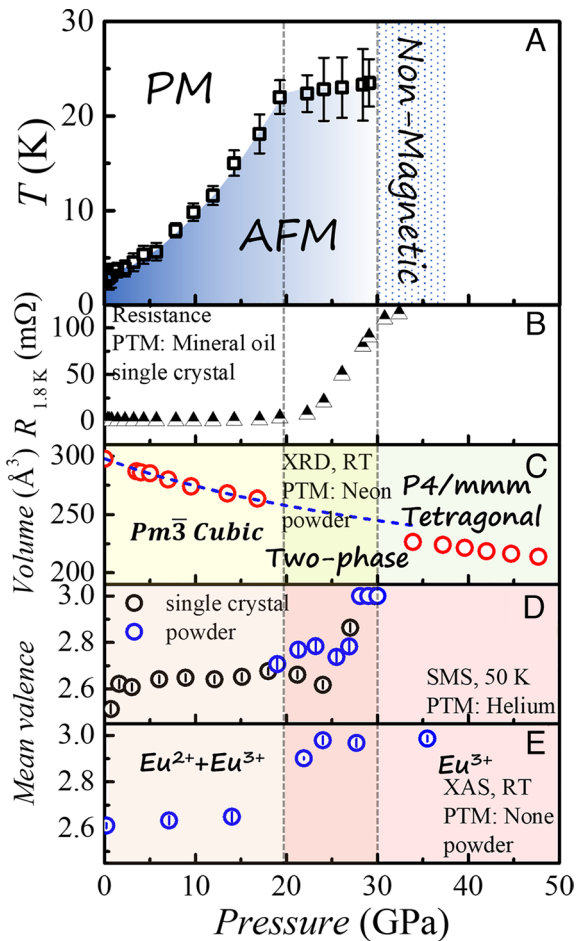

**Fig. 5.** Pressure dependence of electronic, magnetic, and structural properties of  $\text{EuPd}_3\text{S}_4$ . The pressure dependence of (A) AFM transition temperature  $T_N$ , (B) resistance at 1.8 K, (C) unit cell volume estimated from the high-pressure X-ray diffraction measurement, (D) mean valence estimated from the Synchrotron Mössbauer spectroscopy (SMS) spectra, and (E) mean valence estimated from the partial fluorescence-yield X-ray absorption spectroscopy (PFY-XAS) spectra. PTM: pressure transmitting medium. RT: room temperature. The blue dashed curve in (C) is the second-order BM EOS fitted curve that shows the clear difference in the unit cell volume between zone I and zone III. The vertical dashed lines crossing all panels mark the lower and upper boundaries of the two-phase region determined from X-ray diffraction.

relatively low and essentially unchanging in the low-pressure phase. In the intermediate pressure region,  $R(1.8\text{K})$  rises substantially in a near linear manner before appearing to saturate above 30 GPa. The unit cell volumes for the low-pressure and high-pressure phases are shown in Fig. 5C. In the two-phase region, there is an increasing amount of tetragonal phase as pressure increases. The estimated mean valence derived from SMS results is shown in Fig. 5D. The mean valence is nearly constant up to  $\sim 20$  GPa, increases in a nonmonotonic manner, depending upon the run and sample, over the next 10 GPa and is fully trivalent at and above 30 GPa. The mean valence derived from XAS data in Fig. 5E is fully consistent with the SMS data but suffers from two problems. First, the XAS data is the only dataset collected without pressure medium and as such represents very different pressure conditions; second, the XAS dataset is too sparse to accurately detect an onset to valence change. All of this said, the XAS dataset is qualitatively similar to the SMS data, showing a change from roughly 50:50  $\text{Eu}^{2+}:\text{Eu}^{3+}$  to essentially  $\text{Eu}^{3+}$  by  $\sim 25$  GPa. The fact that this pressure is lower than any seen in the other measurements is most likely associated with the less hydrostatic conditions. Taken all together, then, our diverse datasets are consistent

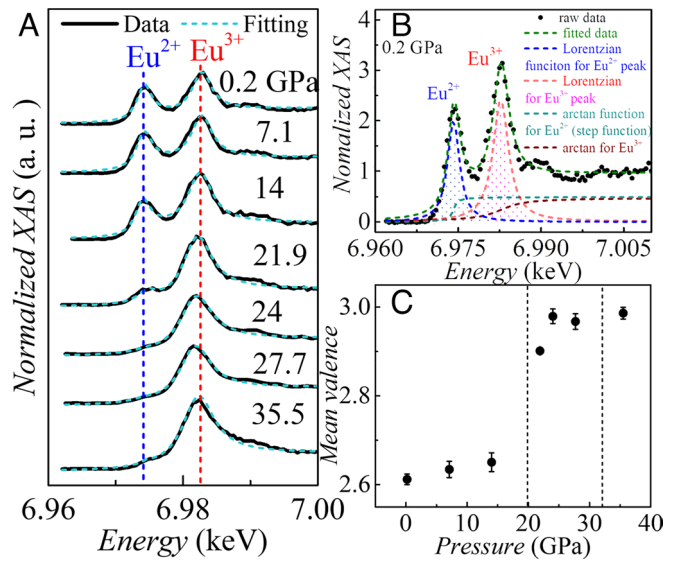

**Fig. 6.** Pressure induced valence transition from absorption spectra. (A) Partial fluorescence yield X-ray absorption spectroscopy (PFY-XAS) data at Eu L3 absorption edge in  $\text{EuPd}_3\text{S}_4$  at room temperature at pressures from 0.2 GPa to 35.5 GPa showing the valence transition from roughly 50:50  $\text{Eu}^{2+}:\text{Eu}^{3+}$  to essentially  $\text{Eu}^{3+}$ . The blue and red vertical dashed lines are guides to the eye showing the absorption peak energies for  $\text{Eu}^{2+}$  and  $\text{Eu}^{3+}$ , respectively. (B) Fits to the 0.2 GPa PFY-XAS data (described in the text). The red dashed line represents the total summation of two arctangent step functions and two Lorentzian peaks. (C) Mean Eu valence as a function of the pressure. The mean valence is estimated by from the ratio of the areas of fitted Lorentzian peaks.

with  $\text{EuPd}_3\text{S}_4$  being in the low-pressure cubic phase up to  $\sim 20$  GPa. In this pressure range there is a large increase in  $T_N$  that we associated with an increasing coupling (or hybridization) between the Eu  $4f$  shell and the conduction electrons. Whereas such large  $dT_N/dP$  values are rather uncommon for rare-earth compounds, similarly large values have been found for some Eu-based intermetallics, such as  $\text{EuIn}_2\text{As}_2$  (22),  $\text{EuSn}_2\text{As}_2$  (23),  $\text{EuSn}_2\text{P}_2$  (24), and  $\text{EuMnBi}_2$  (25).

Ultimately, when the coupling (or hybridization) between the conduction electrons and the Eu- $4f$ -shell becomes sufficiently strong,  $\text{EuPd}_3\text{S}_4$  starts transforming into the high pressure,  $\text{Eu}^{3+}$ -tetragonal phase and enters the two-phase region of the  $T$ - $P$  phase diagram. As more and more of the sample transforms into the smaller volume, tetragonal phase, the residual cubic  $\text{EuPd}_3\text{S}_4$  remains at a more or less constant strain and constant  $T_N$  and  $T^*$ . The pressure range of this two-phase region,  $\sim 20$  to 30 GPa, is fully consistent with change in volume of the unit cells (between cubic and tetragonal) and their pressure derivatives (Fig. 2E). Finally, near 30 GPa, the conversion is complete, and the sample becomes fully tetragonal and fully nonmagnetic  $\text{Eu}^{3+}$ .

The  $\text{EuPd}_3\text{S}_4$   $T$ - $P$  phase diagram differs from the putative “global phase diagram” (26, 27) for Eu-based compounds in several ways. Qualitatively the size of the increase in  $T_N$  for  $\text{EuPd}_3\text{S}_4$  is remarkable, over 800% increase by  $\sim 20$  GPa; this is much larger than seen for other Eu compounds. Quantitatively, the global phase diagram has the second order  $T_N$  line ending in an isostructural, first-order structural phase transition line that has a finite slope and terminates in a critical end point. Whereas,  $\text{EuPd}_3\text{S}_4$  has a structural phase transition from a low-pressure cubic phase to a high-pressure, trivalent, tetragonal phase with an experimentally vertical phase line and an approximately 10 GPa wide, two phase coexistence region. As such, then, a critical end point is impossible. In this sense,  $\text{EuPd}_3\text{S}_4$  is a particularly clean, stable, and well-behaved system that even at ambient conditions exhibits a rare, possibly unique, inhomogeneous mixed-valence state, making it a convenient and powerful test bed

for models of mixed-valent behavior. In addition, the significant departures from the predicted global phase diagrams (26, 27) mean that  $\text{EuPd}_3\text{S}_4$  presents a unique example of pressure-induced, valence collapse. Despite the extensive exploration and continued attention given to Ce- and Yb-based systems, the rich phenomenology of Eu-based systems has remained largely uncharted. Our finding provides a significant prototype within the Eu-based system, revealing distinct behaviors under high pressure, thereby igniting the potential for further in-depth investigations.

## Materials and Methods

**Crystal Growth.** High-quality single crystals of  $\text{EuPd}_3\text{S}_4$  were grown by a two-step solution growth method by adding Eu to a Pd-S melt (28). First, a nominal composition of  $\text{Eu}_5\text{Pd}_{56}\text{S}_{37}$  was loaded into a fritted alumina crucible set (29, 30) and sealed in a fused silica tube. The tube was heated to 1150 °C, held for 8 h, and cooled over 36 h to 1,050 °C, after which the liquid was decanted. The tube was opened, all solidified sulfides and oxides were discarded, and the captured decanted liquid reused in a new crucible set. The second crucible set was again sealed and then warmed to 1,075 °C. After holding for 8 h, the furnace was slowly cooled over 150 h to 900 °C, at which point the remaining solution was decanted. After cooling to room temperature, the crucibles were opened to reveal large, mirror-faceted crystals (28).

The polycrystal samples (used for synchrotron X-ray diffraction, Mössbauer spectroscopy, and X-ray absorption spectroscopy measurements) were prepared by a direct solid-state reaction from a stoichiometric mixture of EuS (99.9%), Pd (99.95%), and S (99.95%) powders (9). The mixture was pressed into a pellet, loaded in an alumina crucible, and sealed in a fused silica tube with a partial pressure of helium gas. The tube was heated to 650 °C over 3 h, held for an hour and then heated to 900 °C over 3 h, and held for 90 h before furnace cooling. The resulting, sintered pellets were checked for phase purity by powder X-ray diffraction and then, as needed, ground, repressed into a pellet, and heated again to 900 °C for further reaction (9).

### High-Pressure Measurements.

**Electrical transport.** Linear four-terminal electrical resistivity measurements were performed in a Diamond Anvil cell (DAC) [Bjcsistar (31)], with 500- $\mu\text{m}$  culet-size standard cut-type Ia diamonds.  $\text{EuPd}_3\text{S}_4$  single crystals were cleaved into 20- $\mu\text{m}$ -thick flakes and cut and polished into 100  $\mu\text{m}$   $\times$  40  $\mu\text{m}$  plates. A single plate was loaded together with a tiny ruby sphere (<10  $\mu\text{m}$  in diameter) into an apertured stainless-steel gasket covered by cubic-BN. Platinum foil was used to create electrodes to connect to the sample. Nujol mineral oil was used as pressure transmitting medium (PTM), since 1) this fluid medium can maintain a quasi-hydrostatic pressure environment with a small pressure gradient below its liquid/glass transition (16, 32, 33), and 2) the use of a fluid medium helps to minimize direct contact between the sample and diamond culet which could lead to an uniaxial pressure component. Pressure was determined by ruby fluorescence (34) at room temperature. Low-temperature resistance measurements down to 1.8 K were conducted in the Quantum Design Physical Property Measurement System (PPMS).

**X-ray Diffraction (XRD).** Two room-temperature high-pressure powder XRD (PXRD) runs were carried out at the GSECARS 13-BM-D and XSD 3-ID-B Beamlines of the Advanced Photon Source (APS), at Argonne National Laboratory (ANL). X-rays with a wavelength of 0.29521 Å and 0.4833 Å were focused to a 15  $\mu\text{m}$  (vertical)  $\times$  15  $\mu\text{m}$  (horizontal) spot size at both beamlines. The sintered powder sample and manometer (ruby spheres for runs 1 and 2, Cu powder for run 3) were loaded into a wide opening SSDAC-70 DAC, diamond anvils with 300  $\mu\text{m}$  and 500  $\mu\text{m}$  diameter culets and Re gaskets were used to contain the sample. Neon was loaded as the PTM. Pressures were determined in situ using the ruby scale (34) or the equation of state of the Cu standard (JCPDS 04-0836) at the same position where the PXRD data were taken on the sample. The two-dimensional diffraction images were integrated using the DIOPTAS software (35) and Rietveld and Le Bail refinements were performed in GSAS-II (36). PXRD data shown in the main text are all from run 3.

**Synchrotron Mössbauer Spectroscopy (SMS).** High-pressure  $^{151}\text{Eu}$  SMS (11) experiments were carried out at 3-ID-B Beamline of the APS, at ANL. SMS, also known as nuclear forward scattering (NFS), utilizes a pulsed synchrotron X-ray source to probe nuclear hyperfine interactions in the time domain rather than the energy

domain used for conventional Mössbauer spectroscopy. The SMS experiments were performed in the 24-bunch timing mode with a 153 ns separation between successive electron bunches. A specially designed helium-flow cryostat cooled the sample to 50 K while high pressures were generated using a membrane-driven miniature panoramic DAC (37). Five hundred micrometer culet size diamonds were used as anvils and a laser drilled Re gasket formed the sample chamber. The SMS spectra were fitted using the CONUSS software package (21).

Both single crystal and sintered powder samples were measured by SMS. All the SMS measurements were performed at 50 K. This temperature was chosen for operational convenience: low enough to benefit from a factor of two increase in the recoil-free fraction ( $f$ -factor) compared with ambient temperatures (9) but high enough to remain above the expected pressure-driven increase in  $T_N$ . Helium was used as PTM to promote hydrostatic conditions at high pressure. After gas loading at room temperature, all subsequent pressure changes were made by the gas membrane at 50 K. Using an online system, laser-excited ruby fluorescence spectra were collected for the determination of pressure using the ruby scale (34). Pressure-induced changes in the europium valence, as well as structure, have been detected through either a change in the isomer shifts of the two preexisting components ( $\text{Eu}^{2+}$  and  $\text{Eu}^{3+}$ ) or changes in their relative proportions. Absolute isomer shift values were obtained at several pressures by adding a reference sample (EuS) with a known isomer shift (−11.496 mm/s relative to  $\text{EuF}_3$ ) in the X-ray beam (38–40).

### Partial Fluorescence-Yield X-ray Absorption Spectroscopy (PFY-XAS).

PFY-XAS experiments were carried out at the 16ID-D Beamline of the APS, at ANL, to provide direct information about the europium valence state and corroborate any possible changes suggested by the isomer shift measurements. The XAS experiment was carried out at Eu  $L_3$  edge (6.97 keV,  $2p_{3/2} \rightarrow 5d$  transition) at pressures up to ~36 GPa. A pair of 300- $\mu\text{m}$  culet diamonds were used as anvils. The sintered powder sample (a small piece in ~50  $\mu\text{m}$  size) was loaded together with a tiny ruby sphere into the aperture of the laser-drilled beryllium gasket and an insert formed by cubic boron nitride and epoxy. No PTM was added with the sample serving as its own transmission medium. As a result, the PFY-XAS measurements are expected to suffer the most from potentially nonhydrostatic effects. Pressures were measured in situ using ruby fluorescence (34). To avoid heavy absorption by the diamond anvils at these low (~7 keV) X-ray energies, the XAS data were taken with the incident beam going through the beryllium gasket and the absorption signal being taken in fluorescence geometry (90° to the incident beam) using a Pilatus detector. The X-rays were focused to 5  $\mu\text{m}$  [the Full Width Half Maximum (FWHM)]. The beam spot location was carefully determined by scanning the sample position to minimize self-absorption.

**Data, Materials, and Software Availability.** All study data are included in the article and/or *SI Appendix*.

**ACKNOWLEDGMENTS.** Work at Ames National Laboratory is supported by the US DOE, Basic Sciences, Material Science and Engineering Division under contract no. DE-AC02-07CH11358. T.J.S. was partially supported by the Center for Advancement of Topological Semimetals (CATS), an Energy Frontier Research Center funded by the US Department of Energy Office of Science, Office of Basic Energy Sciences, through Ames National Laboratory. Work at McGill University is supported by Fonds Québécois de la Recherche sur la Nature et les Technologies and the Natural Sciences and Engineering Research Council (NSERC) Canada; Work at Argonne National Laboratory is supported by the US Department of Energy, Office of Science, under contract no. DE-AC-02-06CH11357. Portions of this work were performed at GeoSoilEnviroCARS (The University of Chicago, Sector 13), Advanced Photon Source (APS), Argonne National Laboratory. GeoSoilEnviroCARS is supported by the NSF–Earth Sciences (EAR-1634415). This research used resources of the Advanced Photon Source, a US Department of Energy (DOE) Office of Science User Facility operated for the DOE Office of Science by Argonne National Laboratory under contract no. DE-AC02-06CH11357. Use of the COMPRES-GSECARS gas loading system was supported by COMPRES under NSF Cooperative Agreement EAR-1606856 and by GSECARS through NSF grant EAR-1634415 and DOE grant DE-FG02-94ER14466. This research used resources of the Advanced Photon Source, a US Department of Energy (DOE) Office of Science User Facility operated for the DOE Office of Science by Argonne National Laboratory under contract no. DE-AC02-06CH11357. Portions of this work were performed at HPCAT (Sector 16), APS, and ANL. HPCAT operations are supported by DOE–NNSA's Office of Experimental Sciences. G.J. and W.B. acknowledge

the support from the NSF CAREER award no. DMR-2045760, and the help from Y. Xiao at APS, ANL, to set up the beamline. W.X. and H.W. are supported by the US Department of Energy (DOE), Office of Science, and Basic Energy Sciences under award DE-SC0023648. P.C.C. would like to thank Richard Olson for having helped enable the completion of this work.

Author affiliations: <sup>a</sup>Ames National Laboratory, US DOE, Iowa State University, Ames, IA 50011; <sup>b</sup>Department of Physics and Astronomy, Iowa State University, Ames, IA 50011; <sup>c</sup>Physics Department and Centre for the Physics of Materials, McGill University, Montreal, QC H3A 2T8, Canada; <sup>d</sup>Center for Advanced Radiation Sources, The University of Chicago, Chicago, IL 60637; <sup>e</sup>Advanced Photon Source, Argonne National Laboratory, Argonne, IL 60439; <sup>f</sup>Department of Physics, University of Alabama at Birmingham, Birmingham, AL 35294; and <sup>g</sup>Department of Chemistry, Michigan State University, East Lansing, MI 48824

1. C. M. Varma, Mixed-valence compounds. *Rev. Mod. Phys.* **48**, 219 (1976).
2. J. Arvanitidis, K. Papagelis, S. Margadonna, K. Prassides, A. N. Fitch, Temperature-induced valence transition and associated lattice collapse in Samarium fulleride. *Nature* **425**, 599–602 (2003).
3. M. M. Abd-Elmeguid, Ch. Sauer, W. Zinn, Pressure-induced valence change of Eu in  $\text{Eu}(\text{Pd}_{0.8}\text{Au}_{0.2})_2\text{Si}_2$ : Collapse of magnetic order. *J. Phys. Chem. B* **101**, 2467 (1997).
4. Y. Matsumoto *et al.*, Quantum criticality without tuning in the mixed valence compound  $\beta\text{-YbAlB}_4$ . *Science* **331**, 316 (2011).
5. M. Okawa *et al.*, Strong valence fluctuation in the quantum critical heavy fermion superconductor  $\beta\text{-YbAlB}_4$ : A hard X-ray photoemission study. *Phys. Rev. Lett.* **104**, 247201 (2010).
6. M. Dzero, M. R. Norman, I. Paul, C. Pépin, J. Schmalian, Quantum critical end point for the kondo volume collapse model. *Phys. Rev. Lett.* **97**, 185701 (2006).
7. M. Wakeshima, Y. Doi, Y. Hinatsu, N. Masaki, Mössbauer effects and magnetic properties of mixed valent europium sulfide,  $\text{EuPd}_3\text{S}_4$ . *J. Solid State Chem.* **157**, 117 (2001).
8. P. Bonville *et al.*, Heterogeneous mixed valence in  $\text{YbPd}_3\text{S}_4$ : Evidence from  $^{170}\text{Yb}$  Mössbauer and x-ray  $L_{II}$ -edge absorption measurements. *J. Phys.: Condens. Matter* **15**, L263 (2003).
9. D. H. Ryan, S. L. Bud'ko, B. Kuthanazhi, P. C. Canfield, Valence and magnetism in  $\text{EuPd}_3\text{S}_4$  and  $(\text{Y}, \text{La})\text{xEu}_{1-x}\text{Pd}_3\text{S}_4$ . *Phys. Rev. B* **107**, 014402 (2023).
10. T. Berry *et al.*, Formation of a simple cubic antiferromagnet through charge ordering in a double Dirac material. *arXiv [Preprint]* (2023). <https://doi.org/10.48550/arXiv.2303.02218>.
11. R. Lübbbers, G. Wortmann, H. F. Grünsteudel, High-pressure studies with nuclear scattering of synchrotron radiation. *Hyperfine Interactions* **123**, 529–559 (1999).
12. B. K. Cho, J.-S. Rhyee, J. Y. Kim, M. Emilia, P. C. Canfield, Anomalous magnetoresistance at low temperatures in a single crystal of  $\text{GdB}_4$ . *J. Appl. Phys.* **97**, 10A923 (2005).
13. J. Y. Kim *et al.*, Magnetic anisotropy and magnon gap state of  $\text{SmB}_4$  single crystal. *J. Appl. Phys.* **107**, 09E111 (2010).
14. C. Hermann, Zur systematischen Strukturtheorie. IV. Untergruppen. *Z. Kristallogr.* **69**, 533 (1929).
15. S. Deonaraine, J. L. Birman, Group-subgroup phase transitions, Hermann's space-group decomposition theorem, and chain subduction criterion in crystals. *Phys. Rev. B* **27**, 4263 (1983).
16. S. Klotz, J.-C. Chervin, P. Munsch, G. Le Marchand, Hydrostatic limits of 11 pressure transmitting media. *J. Phys. D Appl. Phys.* **42**, 075413 (2009).
17. A. Jayaraman, V. Narayanamurti, E. Bucher, R. G. Maines, Continuous and discontinuous semiconductor-metal transition in Samarium monochalcogenides under pressure. *Phys. Rev. Lett.* **25**, 368 (1970).
18. A. I. Goldman *et al.*, Lattice collapse and quenching of magnetism in  $\text{CaFe}_2\text{As}_2$  under pressure: A single-crystal neutron and X-ray diffraction investigation. *Phys. Rev. B* **79**, 024513 (2009).
19. P. C. Canfield *et al.*, Structural, magnetic and superconducting phase transitions in  $\text{CaFe}_2\text{As}_2$  under ambient and applied pressure. *Phys. C* **469**, 404–412 (2009).
20. P. W. Anderson, S. T. Chui, Anharmonic strain effects in crystals and mixed valence states. *Phys. Rev. B* **9**, 8 (1974).
21. W. Sturhahn, CONUSS and PHOENIX: Evaluation of nuclear resonant scattering data. *Hyperfine Interact.* **125**, 149–172 (2000).
22. F. H. Yu *et al.*, Elevating the magnetic exchange coupling in the compressed antiferromagnetic axion insulator candidate  $\text{EuIn}_2\text{As}_2$ . *Phys. Rev. B* **102**, 180404(R) (2020).
23. L. Zhao *et al.*, Monoclinic  $\text{EuSn}_2\text{As}_2$ : A novel high-pressure network structure. *Phys. Rev. Lett.* **126**, 155701 (2021).
24. W. Bi *et al.*, Drastic enhancement of magnetic critical temperature and amorphization in topological magnet  $\text{EuSn}_2\text{P}_2$  under pressure. *npj Quantum Mater.* **7**, 43 (2022).
25. R. A. Susilo *et al.*, Impacts of pressure to the structural, electronic and magnetic properties of Dirac semimetal  $\text{EuMnBi}_2$ . *Phys. Rev. Res.* **3**, 043028 (2021).
26. Y. Ōnuki, M. Hedo, F. Honda, Unique electronic states of Eu-based compounds. *J. Phys. Soc. Jpn.* **89**, 102001 (2020).
27. C. U. Segre *et al.*, Valence instability in  $\text{Eu}(\text{Pd}_{1-x}\text{Au}_x)_2\text{Si}_2$ : The global phase diagram. *Phys. Rev. Lett.* **49**, 1947 (1982).
28. T. J. Slade, P. C. Canfield, Use of refractory volatile element deep eutectic regions to grow single crystalline intermetallic compounds. *Z. Anorg. Allg. Chem.* **10**, 1002 (2022).
29. P. C. Canfield, T. Kong, U. S. Kaluarachchi, N. H. Jo, Use of frit-disc crucibles for routine and exploratory solution growth of single crystalline samples. *Philos. Mag.* **96**, 84–92 (2016).
30. Canfield Crucible Sets, <https://www.lspceramics.com/canfield-crucible-sets-2>.
31. Bjscistar, [http://www.bjscistar.com/page169?product\\_id=127](http://www.bjscistar.com/page169?product_id=127).
32. A. Celeste, F. Borondics, F. Capitani, Hydrostaticity of pressure-transmitting media for high pressure infrared spectroscopy. *High Pressure Res.* **39**, 608–618 (2019).
33. D. D. Ragan, D. R. Clarke, D. Schiferl, Silicone fluid as a high-pressure medium in diamond anvil cells. *Rev. Sci. Instrum.* **67**, 494–496 (1996).
34. G. Shen *et al.*, Toward an international practical pressure scale: A proposal for an IPPS ruby gauge (IPPS-Ruby2020). *High Press. Res.* **40**, 299–314 (2020).
35. C. Prescher, V. B. Prakapenka, DIOPTAS: A program for reduction of two-dimensional X-ray diffraction data and data exploration. *High Press. Res.* **35**, 223–230 (2015).
36. B. H. Toby, R. B. Von Dreele, GSAS-II: The genesis of a modern open-source all-purpose crystallography software package. *J. Appl. Crystallogr.* **46**, 544–549 (2013).
37. J. Y. Zhao *et al.*, A compact membrane-driven diamond anvil cell and cryostat system for nuclear resonant scattering at high pressure and low temperature. *Rev. Sci. Instrum.* **88**, 125109 (2017).
38. G. Wortmann, U. Ponkratz, B. Bielemeier, K. Rupprecht, Phonon density-of-states in bcc and hcp Eu metal under high pressure measured by  $^{151}\text{Eu}$  nuclear inelastic scattering of synchrotron radiation. *High Press. Res.* **28**, 545–551 (2008).
39. N. M. Souza-Neto *et al.*, Reentrant valence transition in  $\text{EuO}$  at high pressures: Beyond the bond-valence model. *Phys. Rev. Lett.* **109**, 026403 (2012).
40. W. Bi *et al.*, Microscopic phase diagram of  $\text{Eu}(\text{Fe}_{1-x}\text{Ni}_x)\text{As}_2$  ( $x = 0, 0.04$ ) under pressure. *Phys. Rev. B* **103**, 195135 (2021).